

# Repair Application Procedures

ICRI's mission is: ... *to be a leading resource for education and information to improve the quality of repair, restoration, and protection of concrete and other structures.* Part of becoming the leading resource is knowing what other organizations have developed on the topic of concrete repair and, where applicable, to make this information available to our members.

As readers of the *Concrete Repair Bulletin* know, ICRI has been publishing Repair Application Procedures (RAP) Bulletins, developed by the American Concrete Institute (ACI). ICRI has published the first three and, in this issue, because of the pertinent subject matter, we decided to skip ahead and publish Number 8. These Bulletins are "how-to" documents for commonly used concrete repairs. ACI is allowing ICRI to publish them in the *CRB*, as they are of great benefit to our

members. These documents are also available, free of charge, for a limited time on ACI's website: [www.concrete.org](http://www.concrete.org).

Each bulletin gives a concise description of the repair method, including the purpose of the repair, when it should be used, needed surface preparation, material and equipment selection, and safety considerations. Step-by-step procedures are also included to help repair technicians do their jobs correctly. These bulletins are useful reference documents for facility owners, design professionals, and concrete repair contractors.

Users are encouraged to tear out these pages for handy reference, or if you prefer, download these documents from ACI's website, make copies for distribution to your field personnel, and file them for future reference.

## Installation of Embedded Galvanic Anodes

Reported by ACI Committee E 706

David W. Whitmore,<sup>\*\*\*</sup> Chair

J. Christopher Ball\*  
Peter H. Emmons\*\*  
Timothy R. W. Gillespie  
H. Peter Golter

Fred R. Goodwin  
Bob Joyce  
Brian F. Keane  
Kenneth M. Lozen  
John S. Lund

Kelly M. Page  
Jay H. Paul  
George I. Taylor  
Patrick M. Watson\*\*\*\*

\*Primary author of RAP Bulletin No. 6

\*\*Primary author of RAP Bulletin No. 7

\*\*\*Primary author of RAP Bulletin No. 8

\*\*\*\*Primary author of RAP Bulletin No. 9

*The committee would like to thank Brandon Emmons for his illustrations in these bulletins.*

It is the responsibility of the user of this document to establish health and safety practices appropriate to the specific circumstances involved with its use. ACI does not make any representations with regard to health and safety issues and the use of this document. The user must determine the applicability of all regulatory limitations before applying the document and must comply with all applicable laws and regulations, including but not limited to, United States Occupational Safety and Health Administration (OSHA) health and safety standards.

### Structural Disclaimer

This document is intended as a voluntary field guide for the Owner, design professional, and concrete repair contractor. It is not intended to relieve the user of this guide of responsibility for a proper condition assessment and structural evaluation of existing conditions, and for the specification of concrete repair methods, materials, or practices by an experienced engineer/designer.

ACI Repair Application Procedure 8.

Copyright © 2005, American Concrete Institute.

All rights reserved including rights of reproduction and use in any form or by any means, including the making of copies by any photo process, or by electronic or mechanical device, printed, written, or oral, or recording for sound or visual reproduction or for use in any knowledge retrieval system or device, unless permission in writing is obtained from the copyright proprietors. Printed in the United States of America.

The Institute is not responsible for the statements or opinions in its publications. Institute publications are not able nor intended to supplant individual training, responsibility or judgment of the user, or the supplier of the information provided.



ACI RAP Bulletin 8

American Concrete Institute®

FIELD GUIDE TO  
CONCRETE REPAIR  
APPLICATION PROCEDURES

# Installation of Embedded Galvanic Anodes

*by David Whitmore*



## Introduction

In the last 20 years, there has been an increase in the need for concrete rehabilitation. In many structures, exposure to deicing chemicals and marine-sourced chloride is a significant cause of corrosion, playing a more detrimental role than originally anticipated. Corrosion of reinforcing steel within concrete is recognized as a significant problem facing present-day owners and engineers.

The most common procedure for repairing deteriorated concrete involves the removal of the damaged material and replacement with new concrete or mortar. While this addresses the immediate serviceability requirements, it does not always satisfy long-term durability needs. Differences in pH, porosity, and chloride content are a few of the factors that may result in corrosion activity. As a result, “chip and patch-style” repairs may fail prematurely in chloride-exposed structures.

Repair of corrosion-related deterioration in concrete structures offers unique challenges. In particular, the “ring-anode” effect, also called the “halo” effect (Fig. 1), is a phenomenon that is frequently overlooked but is a common cause of premature patch failure or increased repair volume. Generally stated, the ring-anode effect describes the increase in corrosion activity adjacent to a repair area. The ring-anode effect is caused by the electrochemical incompatibility between reinforcing steel within a patch and the steel embedded within the surrounding concrete.

**Galvanic technology**—Galvanic methods of corrosion protection have been developed for use in concrete. These methods are used to combat the underlying corrosion rather than simply repairing the physical damage. By supplying a small electrical current to the reinforcing steel, one can slow down corrosion of the steel. Galvanic systems are desirable because they create their protective current internally through a natural reaction wherein the anode corrodes to galvanically protect the reinforcing steel.

**Embedded galvanic anodes**—Embedded galvanic anodes are installed by burying them within the concrete. Type 1 embeddable galvanic anodes are available to be included in standard concrete repair (Fig. 2) or along a joint between new and existing concrete. Type 2 embeddable galvanic anodes are designed to be installed in sound concrete (Fig. 3). When Type 1 anodes are included in a concrete repair, they are typically installed at the perimeter of a repair area to be in the immediate area of concern. When a suitable concrete or mortar is placed around the anode, it begins to sacrificially protect the adjacent reinforcement.

### What is the purpose of this repair?

Embedded galvanic anodes reduce the corrosion activity of the reinforcing steel in the vicinity of the installed anode. Anodes are installed in areas of the concrete where there is a high likelihood of corrosion occurring or recurring. Type 1 anodes are installed to provide improved protection of reinforcing steel in chloride-contaminated or carbonated concrete surrounding a patch repair. Type 2 anodes are used in sound chloride-contaminated or carbonated concrete to prevent the onset of delamination or spalling of the concrete.

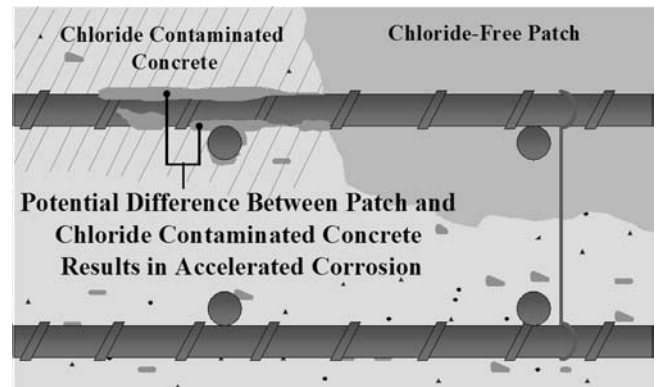


Fig. 1—“Ring-anode” corrosion.

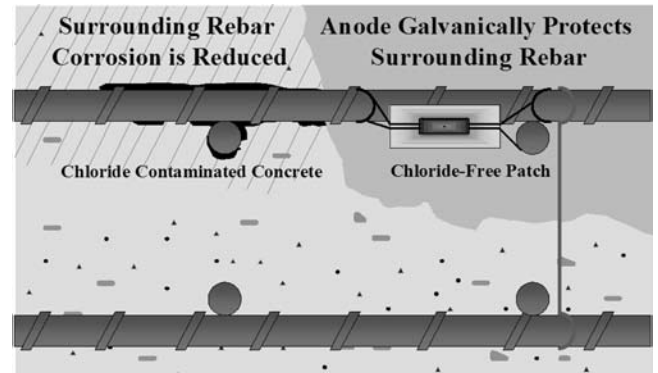


Fig. 2—Chloride-accelerated corrosion.

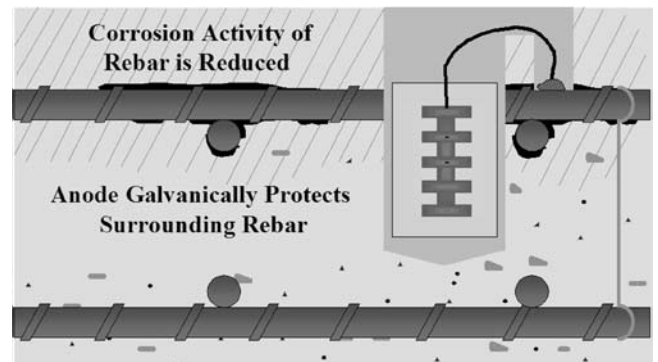


Fig. 3—Chloride-accelerated corrosion.

### When do I use this method?

Embedded galvanic anodes are attached to reinforcing steel within the patch cavity to protect the steel in concrete adjacent to the patch. For repairs in either chloride-contaminated or carbonated concrete, embedded galvanic anodes can be incorporated in the repair to minimize corrosion of the reinforcing steel adjacent to the repair. Embedded galvanic anodes can also be attached to reinforcement at the interface of new and existing chloride-contaminated concrete. Examples of uses include bridge deck widening, replacement of deck joint nosings, or concrete pile jacketing.

During concrete condition inspections, areas of potentially active corrosion of the reinforcing steel are often discovered in mechanically sound concrete. Embedded galvanic anodes can be installed in these areas to delay corrosion damage to the concrete. These anodes can be installed on a grid pattern over

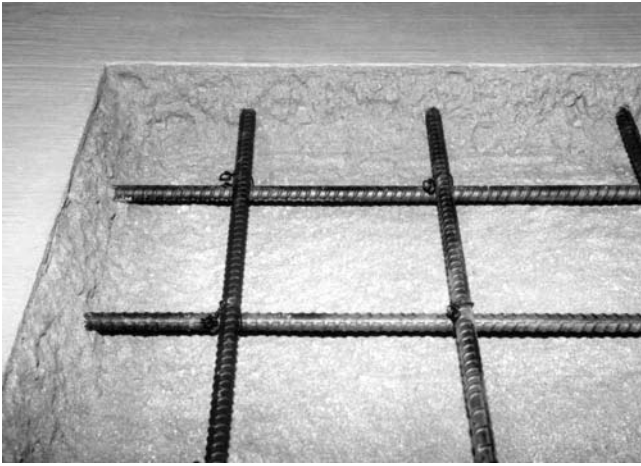


Fig. 4—Deteriorated concrete removed.

a large area to provide protection for reinforcing steel in concrete that is found to be or is suspected to be contaminated.

### How do I prepare the surface?

Complete surface preparation as required for the application of the repair concrete or mortar. Limit the use of bonding agents to those with low resistivity, such as slurries containing portland cement or portland cement-sand mixtures. Avoid insulating materials such as epoxy bonding agents.

### How do I select the right material?

Embedded galvanic anodes should be used only in conjunction with cementitious or cementitious-polymer repair materials, which have a low resistivity. Resistivity of repair materials or concrete for use with embedded galvanic anodes should be less than 15,000 ohm-cm. High-resistivity materials such as epoxies or highly polymer modified repair mortars greatly reduce the available galvanic current or prevent the anodes from functioning properly. If a low-resistivity material is not suitable for the full repair, anodes can be embedded in individual pockets of low-resistivity material. These pockets should completely encapsulate the anode and completely fill the space between the anode and the concrete substrate.

### What equipment do I need?

The equipment needed to install Type 1 embedded galvanic anodes in standard repairs entails only basic hand tools and a DC ohm meter capable of reading 0 to 200 ohms. To install Type 2 embedded galvanic anodes in sound concrete, the equipment required includes a reinforcing bar locator, percussion drill or core drill, basic hand tools, and DC ohm meter.

### What are the safety considerations?

It is the responsibility of the user of this document to establish health and safety practices appropriate to the specific circumstances involved with its use. ACI does not make any representations with regard to health and safety issues and the use of this document. The user must determine the applicability of all regulatory limitations before applying the document and must comply with all applicable laws and

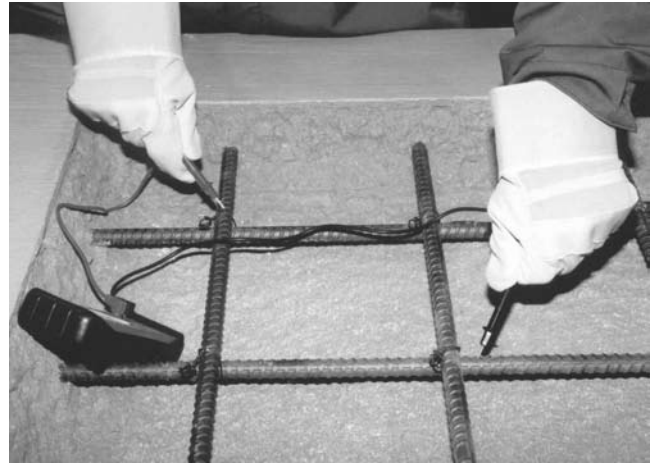


Fig. 5—Checking continuity of reinforcing steel.

regulations including, but not limited to, United States Occupational Safety and Health Administration (OSHA) health and safety standards.

### Preconstruction meeting

Prior to proceeding with the repair, a preconstruction meeting is recommended. The meeting should include representatives from all participating parties (owner, engineer, contractor, materials manufacturer, etc.), and specifically address the parameters, means, methods, and materials necessary to achieve the repair objectives.

### Repair procedure

Anode spacing in either repair type is often determined by the engineer, and differs for each situation. Spacing of the anodes is mainly a function of steel density and the corrosiveness of the environment. Structures with heavy reinforcement or structures in highly corrosive environments often require closer spacing for the anodes to function effectively.

*Type 1 embedded anodes installed in standard repairs—*As in standard patch repairs, all deteriorated concrete should be removed from around and behind the reinforcing steel inside the repair area in accordance with good concrete repair practice (Fig. 4). Sufficient clearance between the anode and the substrate concrete should be provided (minimum of 3/4 in. [19 mm] or 1/4 in. [6 mm] larger than the nominal maximum size of the coarse aggregate used in the repair material, whichever is greater). The exposed reinforcing bar in the repair area should be thoroughly cleaned and at least the visible surfaces should be cleaned to a bright metal surface to facilitate good electrical connections where the anodes are attached. Prior to installation, electrical continuity of the reinforcing bar within the repair area should be confirmed with the use of a DC ohm meter (Fig. 5).

Anode spacing is as specified by the engineer, with the anodes placed along the perimeter of the repair area. Each anode should then be securely connected to the reinforcing steel (Fig. 6 and 7). If less than 1 in. (25 mm) of cover exists, the anode should be placed beneath the bar (away from the surface of the concrete). Once installed, the electrical

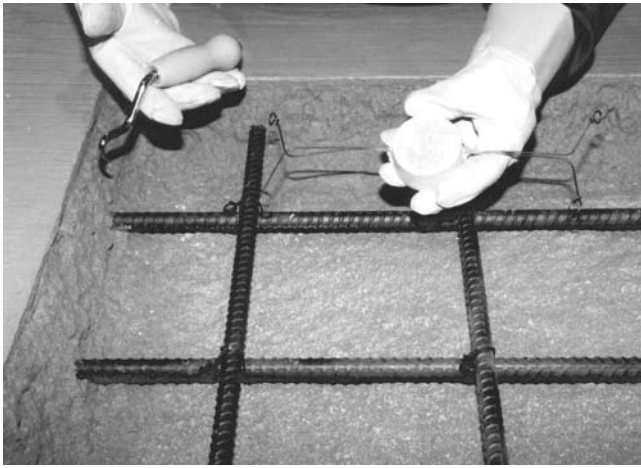


Fig. 6—Tying tool and anode.

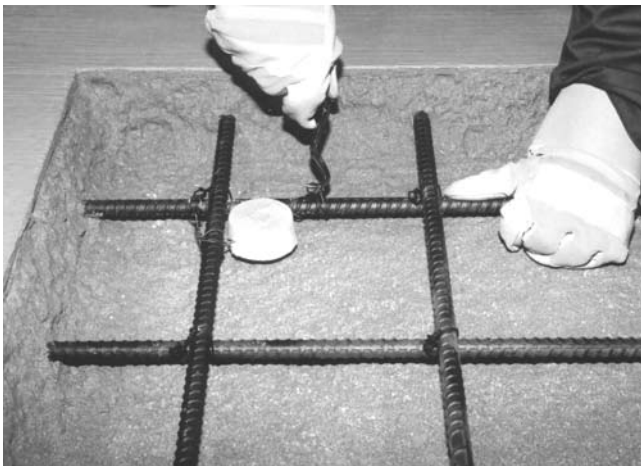


Fig. 7—Tying in anode.

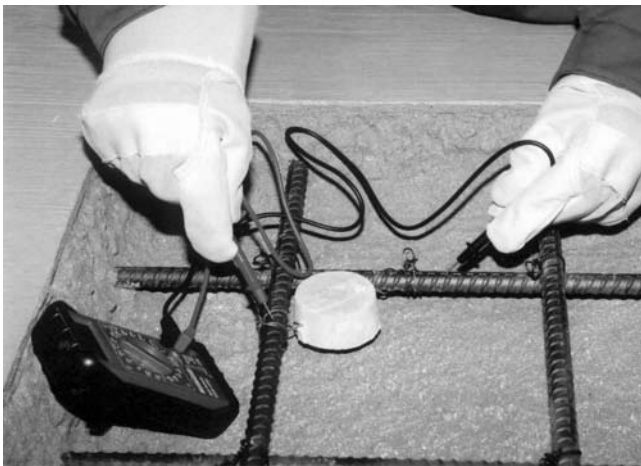


Fig. 8—Confirming connection to reinforcing steel.

connection between the anode and the reinforcing steel should be confirmed (Fig. 8). The resistance of the electrical connection should be less than 1 ohm. Finally, the patch cavity is filled with a compatible repair material, using normal patching procedures and taking care to completely encase the anode.

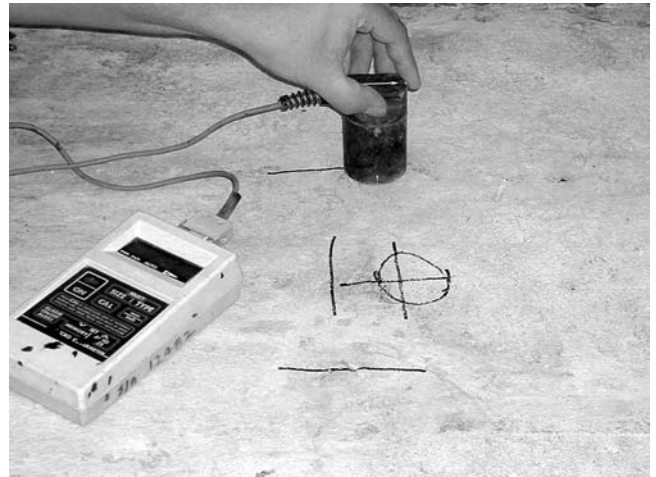


Fig. 9—Locating reinforcing steel.



Fig. 10—Coring hole for anode.



Fig. 11—Secondary hole with reinforcing steel connection.

*Type 2 embedded anodes installed in sound concrete*—Reinforcing steel in the area of the desired installation should be located and marked on the concrete surface (Fig. 9). Based on the location of the reinforcing steel, the anode location should be marked, and a hole of appropriate size should be drilled to accommodate the anode (Fig. 10). A location for connection of the anode to the reinforcing steel should then be marked, drilled if necessary, and a connection made (Fig. 11), either within the original hole or in a secondary

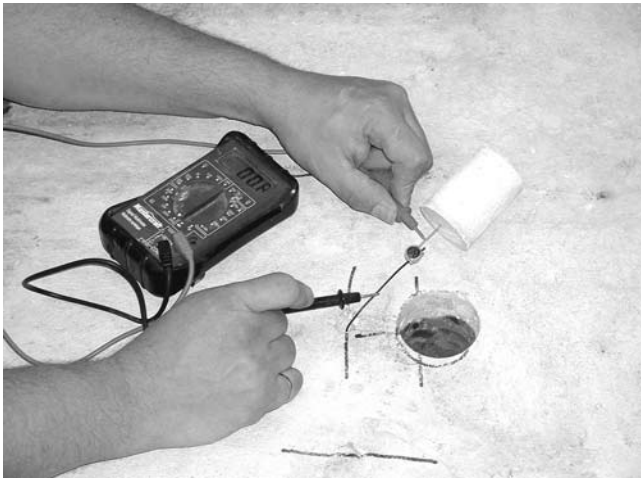


Fig. 12—Confirming connection to reinforcing steel.

hole. Continuity of the reinforcing steel in the location of installation should be verified with a DC ohm meter.

All holes should be cleaned of debris and dust. The anode should be securely connected to the reinforcing steel, and the contact should be confirmed using the DC ohm meter (Fig. 12). Connection resistance should be less than 1 ohm. Any connections between dissimilar metals (such as copper wires to steel) should be sealed with silicone or a two-part epoxy to prevent localized corrosion. The drilled hole(s) can then be filled using the appropriate repair material (Fig. 13).

### How do I check the repair?

Embedded galvanic anodes, when normally installed, allow for very few direct measurements other than those for corrosion potentials. If more-detailed performance data are desired, anodes can be installed to allow monitoring of the current and voltage output of the anodes. With a switch installed in the circuit, corrosion potential or corrosion



Fig. 13—Anode placed in hole with patching material.

potential decay measurements can also be taken, if appropriate, to determine the level of polarization of the steel.

### Sources for additional information

ACI Committee 222, 2001, "Protection of Metals in Concrete Against Corrosion (222R-01)," American Concrete Institute, Farmington Hills, Mich., 41 pp.

ACI Committee 546, 2004, "Concrete Repair Guide (ACI 546R-04)," American Concrete Institute, Farmington Hills, Mich., 53 pp.

Bertolini et al., 1998, "Cathodic Protection and Cathodic Prevention in Concrete: Principles and Applications," *Journal of Applied Electrochemistry*, V. 28, pp. 1321-1331.

Glass, G.; Taylor, J.; Roberts, A.; and Davison, N., 2003, "The Protective Effects of Electrochemical Treatment in Reinforced Concrete," *NACE Paper No. 03291*, Corrosion 2003.

Glass, G.K.; Hassenein, A.M.; and Buenfeld, N.R.; *Corrosion Science*, V. 43, No. 6, 2001, pp. 1111-1131.

Hausman, D. A., 1967, "Steel Corrosion in Concrete," *Material Protection*, pp. 19-23.

International Concrete Repair Institute, 1995, "Guide for Surface Preparation for the Repair of Deteriorated Concrete Resulting from Reinforcing Steel Corrosion," *ICRI Technical Guideline No. 03730*, 5 pp.